UCRL-10919

University of California

Ernest O. Lawrence Radiation Laboratory

TWO-WEEK LOAN COPY

This is a Library Circulating Copy which may be borrowed for two weeks. For a personal retention copy, call Tech. Info. Division, Ext. 5545

TEMPERATURE DEPENDENCE OF FLOW STRESSES ON THE {100} AND {110} PLANES IN LiF, AND THE PLASTICITY OF POLYCRYSTALS

Berkeley, California

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

Journal American Ceramic Society
(Discussions and Notes section)

UCRL-10919

UNIVERSITY OF CALIFORNIA

Lawrence Radiation Laboratory
Berkeley, California

Contract No. W-7407-eng-48

TEMPERATURE DEPENDENCE OF FLOW STRESSES ON THE {100} AND {110} PLANES IN LiF, AND THE PLASTICITY OF POLYCRYSTALS

D. W. Budworth and Joseph A. Pask

August 26, 1963

TEMPERATURE DEPENDENCE OF FLOW STRESSES ON THE {100} AND {110} PLANES IN LiF, AND THE PLASTICITY OF POLYCRYSTALS

D. W. Budworth and Joseph A. Pask

Ceramic Laboratories, Department of Mineral Technology, and
Inorganic Materials Research Division, Lawrence Radiation Laboratory
University of California, Berkeley, California

August 26, 1963

Recent studies of stress-strain curves obtained in bend tests of large-grained polycrystalline LiF showed that a marked increase in plasticity occurred in the temperature range 350 to 400° C.[1] This effect was attributed to the drastic lowering of the flow stress on the {100} ⟨110⟩ family of slip systems which has been shown to occur in this temperature range.[2] It has been found experimentally at room temperature that the {110} ⟨110⟩ family of slip systems is unable alone to provide enough independent systems for polycrystalline plasticity,[3] and it has recently been shown theoretically that movement on both families is required.[4]

Two sets of experiments have been made in an attempt to study this effect more precisely. Polycrystalline specimens have been studied in compression, which enables more accurate values of stress and strain to be attached to the deformation curves than is the case with bend tests; and compression studies of single crystals have been made in order to determine the flow stress on the {110} ⟨110⟩ and {100} ⟨110⟩ families of slip systems as a function of temperature. Gilman[2] has published some such curves but did not extend his measurements below 225° C for the {100} ⟨110⟩ family, or above 220° C for the {110} ⟨110⟩ family. Phillips[5] has published data for the {110} ⟨110⟩ family from -196° C to 600° C but did not study the {100} ⟨110⟩ family.

The polycrystalline specimens were made by crystallization from the melt as previously described[3,1] and measured approximately 3/16 x 3/8 x 1 in. They were polished in phosphoric acid before testing.[3,1] The compression apparatus was of the constant loading rate type, and is to be fully described elsewhere.[6] The load was applied by a calibrated water flow into a bucket attached to a lever system; although constant for a given test, the loading rate varied from about 12 to 20 psi/min. The strain was measured by another lever device: two pivoted, pointed, spring-loaded sapphire rods engaged in two shallow divots 1/2 in. apart in the specimen, and the other ends of the rods operated a linear differential transformer whose output was fed into a pen recorder and used as a measure of strain.

Owing to the large grain size of the polycrystalline specimens it was found that the yield stress depended on the precise orientation of the most favorably oriented grain, and a better quantitative measure of behavior was provided by noting the stress necessary to produce 2% deformation. A plot of this stress as a function of temperature is given in Fig. 1; it can be seen that a distinct step in the curve occurs between 350° C and 400° C and that it tends to extrapolate to zero or a very low stress at the melting temperature of 842° C. The stress-strain curves themselves were similar in appearance to those obtained in bending;[1] the ones at 400° C and higher exhibited a sharp yield, lower work-hardening, and considerably more strain at fracture.

For the single-crystal experiments, two blocks of lithium fluoride* (each 1-1/2 x 1-1/2 x 1 in.) were purchased from the Harshaw Chemical Company, one with {100} faces, the other with the two large faces close

*A spectrographic analysis of the lithium fluoride specimens indicated impurities of 0.002% Mg, 0.0005% Ca, 0.002% Fe, 0.001% Cu, and less than 0.001% Al.

to $\{111\}$ orientation. The latter block was reground so that its faces were within 2 min. of arc of the $\{111\}$ orientation. Specimens approximately 1/4 x 1/4 x 1 in. were cut from each of the blocks with a diamond saw and tested in compression. A specimen compressed in the $\langle 100 \rangle$ direction has a shear stress of one-half of the compressive stress on four of the six $\{110\}$ $\langle 110 \rangle$ slip systems, whereas a specimen compressed in the $\langle 111 \rangle$ direction (i.e., perpendicular to the $\{111\}$ faces) has a shear stress of $\sqrt{2}/3$ times the compressive stress on three of the $\{100\}$ $\langle 110 \rangle$ slip systems. The minimum flow stress which could be measured was about 100 psi because a certain minimum load (corresponding to a compressive stress of about 200 psi) had to be maintained on the specimen to prevent the spring loading of the strain device from pushing the specimen from between the alumina loading rams.

The results obtained are displayed in Fig. 2. For the $\langle 111 \rangle$ oriented specimen ($\{100\}$ $\langle 110 \rangle$ slip) the rate of work-hardening was very high, especially at the lower temperatures, and the yields were thus not very well defined. No measurements were therefore made below 200°C for this orientation, but Johnston's observation[7] that at room temperature the flow stress is about 15 times as high on the $\{100\}$ plane as on the $\{110\}$ plane is consistent with the present observations. It can be seen that the flow stress on the $\{110\}$ plane drops only slowly as the temperature is raised, but that the flow stress on the $\{100\}$ plane drops sharply to 400°C and less quickly thereafter. Both curves tend to extrapolate to zero or a very low stress at the melting point, but the flow stress on the $\{100\}$ plane always tends to be higher than that on the $\{110\}$ plane.

It thus appears that, on both experimental and theoretical grounds, genuine ductility in polycrystalline LiF cannot be expected until it is

possible to activate the $\{100\}\langle 110\rangle$ family of slip systems almost as easily as the $\{110\}\langle 110\rangle$ family which for this batch of LiF occurred at about 400° C. Also, it appears that the stress vs temperature curves, obtained in compression at a constant loading rate, for both single crystals and polycrystals tend to extrapolate to zero or a very low stress at the melting point.

ACKNOWLEDGMENTS

Grateful acknowledgment is extended to S. M. Copley for helpful discussions and to N. E. Olson for obtaining some of the stress-strain curves. The writers also wish to thank the U. S. Atomic Energy Commission for their financial support of this work.

FOOTNOTES AND REFERENCES

At the time this work was done the writers were, respectively, lecturer and professor of ceramic engineering, Department of Mineral Technology, University of California at Berkeley. D. W. Budworth is now lecturer, Department of Refractories Technology, University of Sheffield, Sheffield, England.

1. D. W. Budworth and J. A. Pask, "Effect of Temperature on the Plasticity of Polycrystalline Lithium Fluoride," Trans. Brit. Ceram. Soc. (in press).
2. J. J. Gilman, "Plastic Anisotropy of LiF and Other Rock-Salt-Type Crystals," Acta Met., 7 [9] 608-13 (1959).
3. W. D. Scott and J. A. Pask, "Deformation and Fracture of Polycrystalline Lithium Fluoride," J. Am. Ceram. Soc., 46 [6] 284-93 (1963).
4. G. W. Groves and A. Kelly, "Independent Slip Systems in Crystals," Phil. Mag., 8 [89] 877-87 (1963).
5. W. L. Phillips, "Effect of Strain Rate and Temperature on the Stress-Strain Characteristics of NaCl, LiF, and MgO Single Crystals," Trans. Met. Soc. AIME, 224 [6] 434-36 (1962).
6. C. O. Hulse and S. M. Copley, "High Temperature Compressive Deformation Apparati," to be submitted to Bull. Am. Ceram. Soc.
7. W. G. Johnston, private communication.

FIGURE LEGENDS

Fig. 1. Compressive stress needed to produce 2% deformation of polycrystalline LiF as a function of temperature.

Fig. 2. Flow stress on the $\{100\}\langle 110\rangle$ and $\{110\}\langle 110\rangle$ families of slip systems as a function of temperature.

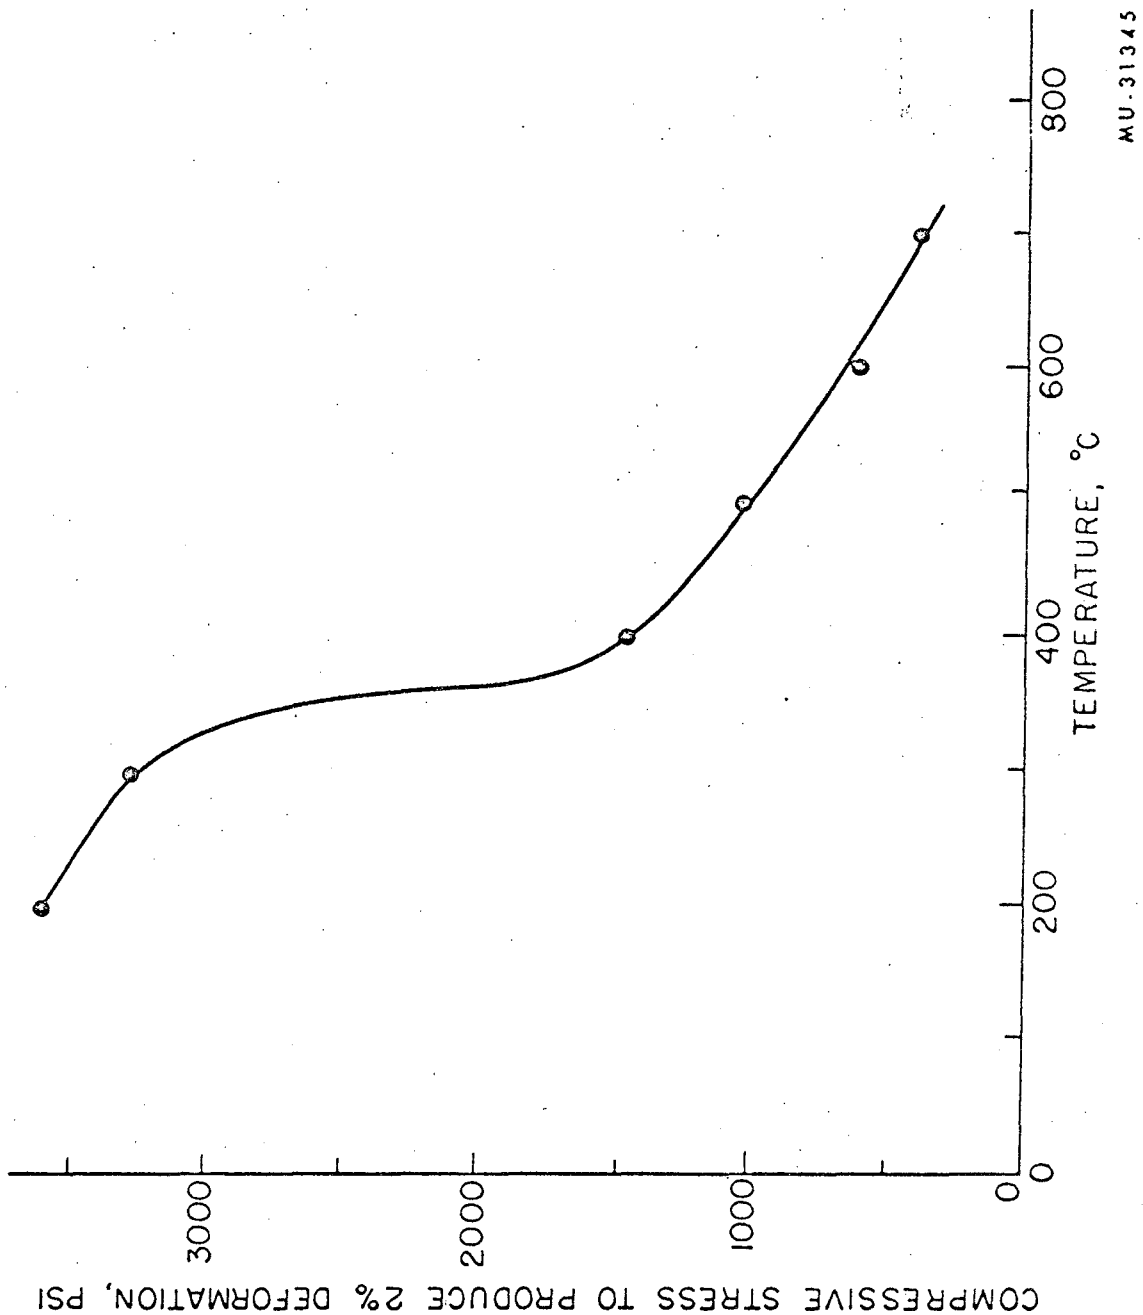
COMPRESSIVE STRESS TO PRODUCE 2% DEFORMATION, PSI
3000
2000
1000
0
0
200
400
600
800
TEMPERATURE, °C
MU-31345

Fig. 1

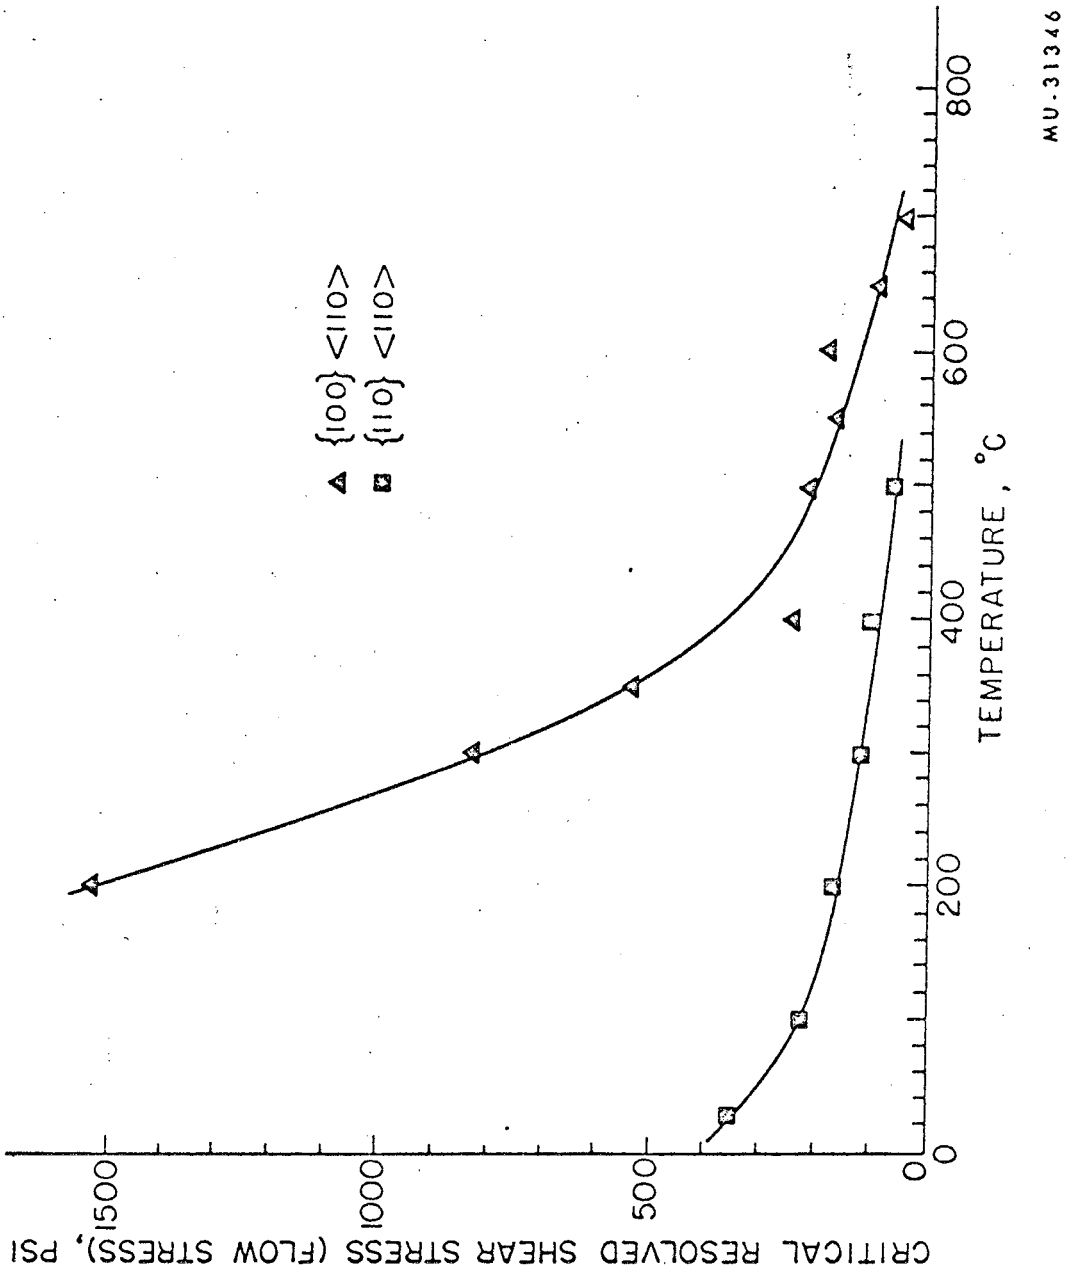
CRITICAL RESOLVED SHEAR STRESS (FLOW STRESS), PSI
1500
1000
500
0
0
200
400
600
800
TEMPERATURE, °C
{100} <110>
{110} <110>
MU-31346

Fig. 2

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or

B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.