UCRL-17026

University of California

Ernest O. Lawrence Radiation Laboratory

A CALORIMETRIC INVESTIGATION OF SUPERCONDUCTIVITY IN α-URANIUM

TWO-WEEK LOAN COPY

This is a Library Circulating Copy which may be borrowed for two weeks. For a personal retention copy, call Tech. Info. Division, Ext. 5545

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

For 10th International Conference on
Low Temperature - Moscow, USSR
August 31 - Sept. 6, 1966
and Proceedings

UCRL-17026
Preprint

UNIVERSITY OF CALIFORNIA

Lawrence Radiation Laboratory
Berkeley, California

AEC Contract No. W-7405-eng-48

A CALORIMETRIC INVESTIGATION OF SUPERCONDUCTIVITY IN α-URANIUM

Norman E. Phillips, James C. Ho and T. F. Smith

July 1966

A Calorimetric Investigation of Superconductivity in α-Uranium*

Norman E. Phillips and James C. Ho

Inorganic Materials Research Division
of Lawrence Radiation Laboratory
and Department of Chemistry
University of California, Berkeley, California

and

T. F. Smith

Department of Physics
and the Institute for the Study of Matter,
University of California, La Jolla, California

Although the occurrence of superconductivity in α-uranium is of particular interest in connection with the role of the 5f states, the relevant experimental evidence is contradictory. Magnetic susceptibility and resistance measurements[1-4] have shown the presence of superconductivity with transition temperatures T_c ranging from 0.2°K to above 1°K, and have also shown an unusually large increase in T_c with pressure.[5] On the other hand, calorimetric measurements on one sample[6] to 0.15°K and on two others[7] to 0.65°K have not shown any indication of a super-

conducting transition. To gain more information about the superconductivity of α-uranium we have made further heat capacity measurements at zero pressure and we have also measured the heat capacity at a pressure of 10 kbar.

At zero pressure, four different samples were investigated. Magnetic measurements were made on three of the samples and showed the presence of broad superconducting transitions in the region of 0.3 to 1.2°K. For each sample the heat capacity was measured in zero field between 0.3°K and 6°K. For two samples the measurements were extended to 0.1°K and for one of these, measurements were made between 0.1 and 1°K in magnetic fields up to 5000 Oe. In addition, 2000-Oe field measurements between 0.3 and 1°K were made on one of the samples that was investigated only above 0.3°K. No sample was the subject of a complete set of measurements, but all the measurements were consistent in showing similar behavior for the different samples. In particular, the heat capacities had qualitatively the same temperature dependence and were unaffected by the applied magnetic fields. Figure 1 shows the measurements below 1.4°K on one sample for which the magnetic measurements showed a broad superconducting transition extending up to 1.2°K. The T^{-2} hyperfine term associated with the U^{235} content was estimated from the lowest-temperature points, which were dominated by this contribution, and has been subtracted from the data in the figure. This accounts for the large scatter in the points below 0.2°K. The other sample measured to 0.1°K had a greatly reduced U^{235} content and showed more clearly that C/T is still increasing with decreasing T at 0.1°K. Above 0.7°K the heat

capacity shows the usual temperature dependence of a normal metal with the coefficient of the electronic term $\gamma = 10.3$ mJ/mole deg^2, but below 0.7°K the heat capacity is anomalously high. This anomaly cannot be associated with the superconducting transition observed magnetically because (a) the same anomaly is found in samples with different magnetically determined transitions, (b) it is unaffected by magnetic fields, and (c) the observed entropy (above 0.1°K) is inconsistent with a superconducting transition. Since none of our measurements show a heat capacity anomaly of the type associated with a bulk superconducting transition, we conclude that T_c for α-uranium is less than 0.1°K and that the magnetically observed transitions are not associated with bulk superconductivity.

The origin of the observed heat capacity anomaly is puzzling. It does not have the T^{-2} temperature dependence expected for nuclear spin ordering, and it is furthermore independent of the U^{235} content (after the appropriate T^{-2} term is subtracted). Since there is some possibility of 5f states' being populated, it is natural to think of ordering of electron spins, but one would then expect the anomaly to be shifted upward in temperature by a 5000-Oe magnetic field, and no such effect was observed.

A part of the sample for which the zero-pressure heat capacity is shown in Fig. 1 was subjected to a pressure of 10 kbar in a specially constructed high-pressure cell and its heat ca- was remeasured. The corrections for the heat capacity of the cell were large, but reasonable accuracy was obtained by using a germanium thermometer that retained its calibration between

the measurements on the filled and empty cell. The results are shown in Fig. 2, where the dashed curve represents the zero-pressure data. There are three striking effects of the pressure: (a) there is a bulk superconducting transition at 2°K, which is in good agreement with magnetic measurements on the same sample, showing that 10 kbar increases T_c by a factor of at least 20, (b) γ is increased by 18%, and (c) the heat capacity anomaly observed at zero pressure is eliminated (or at least reduced).

The BCS expression[8] for T_c is

$$T_c \approx 0.85\,\theta_D \exp[-1/N(0)V],$$

where N(0) is the normal-state density of states (proportional to γ), V measures the strength of the interaction that produces superconductivity, and θ_D is the Debye temperature. To explain an increase in T_c from 0.1 to 2°K, this expression would require a 65% increase in N(0)V. (θ_D is expected to change by no more than 2% and therefore makes a negligible contribution to the change of T_c.) Thus the enhancement of T_c cannot be ascribed to the change in N(0) alone, and a substantial increase in V is implied. Geballe et al[4] have recently suggested that such an enhancement of the superconducting interaction by pressure and the 43°K volume minimum in α-uranium might both be associated with a populating of 5f states below 43°K. This model is supported by analogies with the lanthanide metals: the 4f electrons are known to suppress superconductivity,[9] and the application of pressure to cerium is known to shift electrons out of 4f states.[10] The model also suggests other analogies between the effect of pressure on α-uranium and certain properties of the lanthanides. Heat capacity data[11] for the lantha-

nides indicate that transfer of electrons out of 4f states increases γ, as interpretation of our data in terms of the model would require for the 5f electrons in α-uranium. Furthermore, the heat capacity anomalies[12,13] in cerium associated with ordering of the 4f electrons disappear on application of pressure.[14] On the other hand, cerium does not become superconducting above 0.3°K at 10 kbar,[14] or above 1.2°K at 24 kbar.[15]

We are indebted to a number of our colleagues, in particular to T. H. Geballe, B. T. Matthias, and W. E. Gardner, for stimulating and informative discussions, and to C. E. Olsen for making available several of the samples.

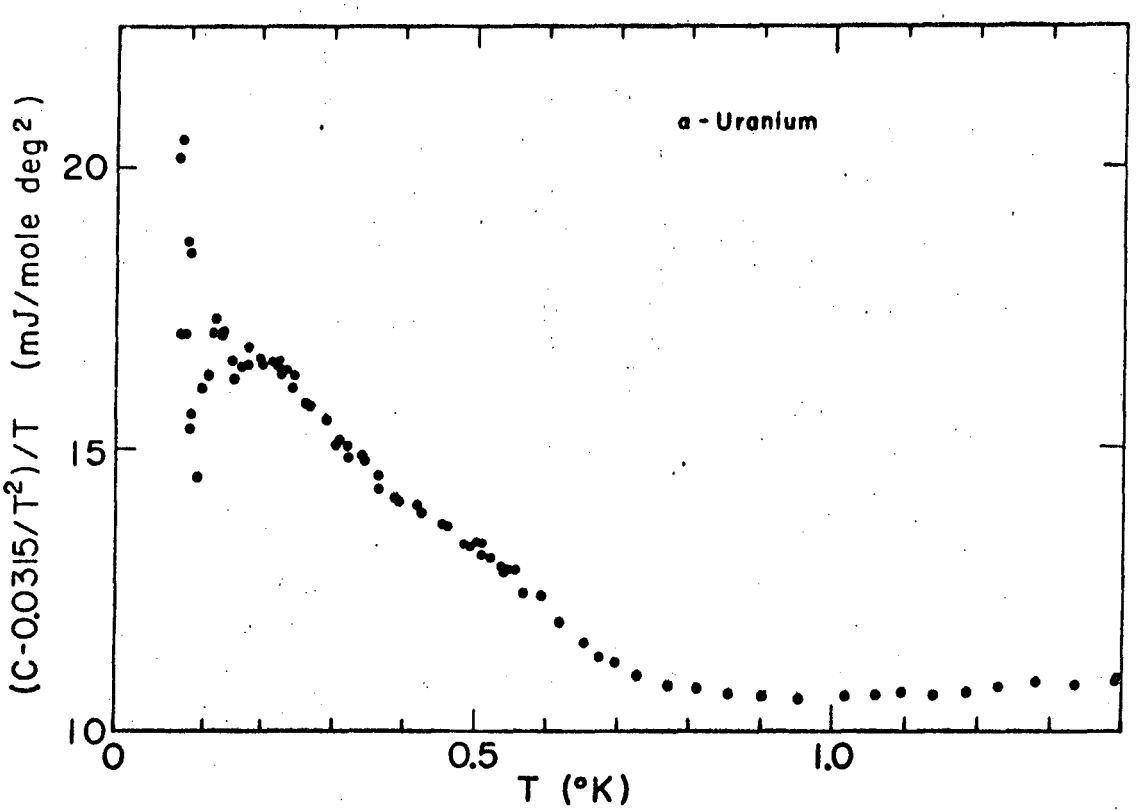

Fig. 1. The heat capacity of α-uranium at zero pressure. The experimental data have been corrected for the hyperfine contribution by subtraction of 0.0315 T^{-2} m/Jmole deg.

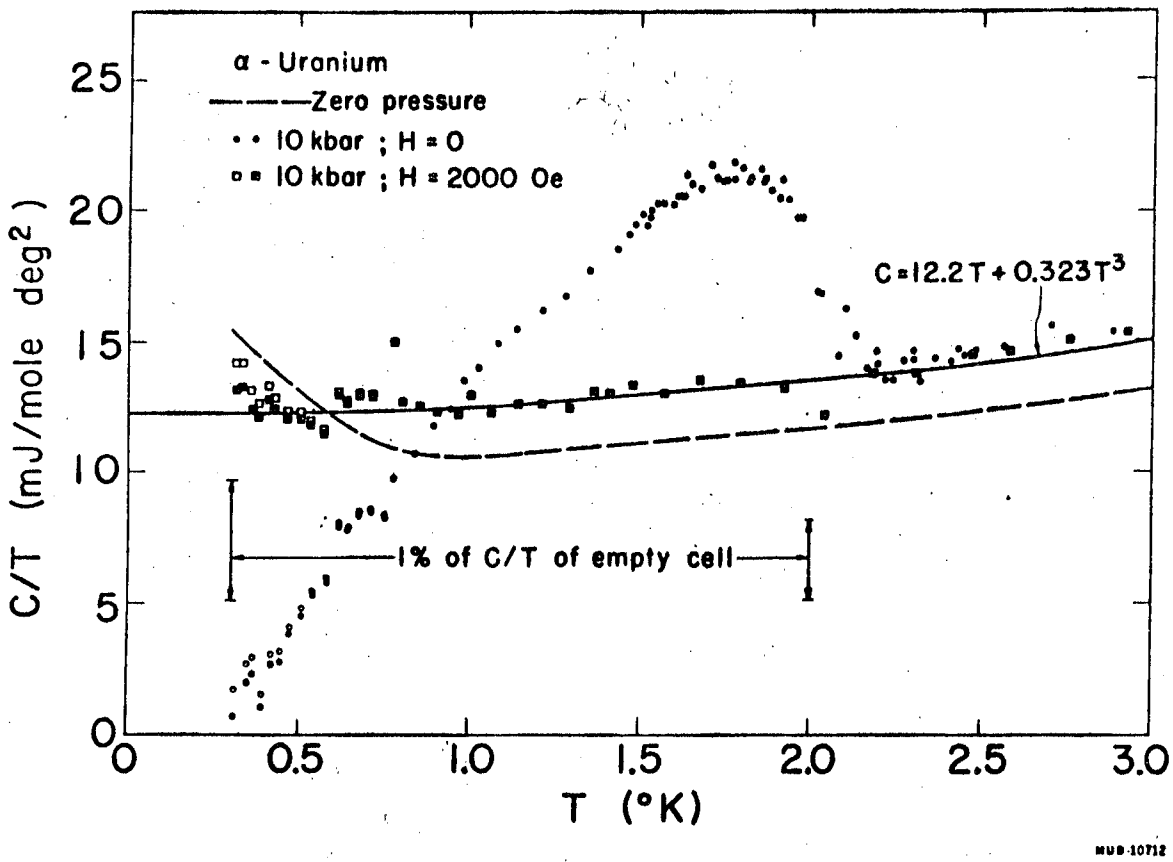

Fig. 2. The heat capacity of α-uranium at zero pressure and at 10 kbar. Points represented by solid symbols and the dashed curve have been corrected for the hyperfine heat capacity by subtraction of a T^{-2} term. The open symbols represent the total sample heat capacity. For $T > 1°K$ the dashed curve corresponds to $C = 10.3\ T = 0.323\ T^3$.

References

*Work supported by the U. S. Atomic Energy Commission and by the U. S. Air Force Office of Scientific Research.

1. B. B. Goodman and D. Shoenberg, Nature 165, 442 (1950).

2. J. E. Kilpatrick, E. F. Hammel, and D. Mapother, Phys. Rev. 97, 1634 (1955).

3. R. A. Hein, W. E. Henry, and N. M. Wolcott, Phys. Rev. 107, 1517 (1957).

4. T. H. Geballe, B. T. Matthias, K. Andres, E. S. Fisher, T. F. Smith, and W. H. Zachariasen, Science 152, 755 (1966).

5. T. F. Smith and W. E. Gardner, Phys. Rev. 140, A1620 (1965).

6. C. W. Dempesy, J. E. Gordon, and R. H. Romer, Phys. Rev. Letters 11, 547 (1963).

7. J. E. Gordon, H. Montgomery, R. J. Noer, G. R. Pickett, and R. Tobón, Phys. Rev. (to be published).

8. J. Bardeen, L. N. Cooper, and J. R. Schrieffer, Phys. Rev. 108, 1175 (1957).

9. B. T. Matthias, H. Suhl, and E. Corenzwit, Phys. Rev. Letters 1, 92 (1958).

10. See K. A. Gschneidner, Jr., and R. Smoluchowski, J. Less Common Metals 5, 374 (1963) for a review of the electronic states of cerium.

11. See K. A. Gschneidner, Jr., Rare Earth Research III, Ed. L. Eyring, (Gordon and Breach, 1965) p. 153 for a review of the experimental data on the density of states of the lanthanides.

12. O. V. Lounasmaa, Phys. Rev. 133, A502 (1964).

13. D. H. Parkinson, F. E. Simon, and F. H. Spedding, Proc. Roy. Soc. (London) A207, 137 (1951).

14. We have also measured the heat capacity of cerium at 10 kbar between 0.3 and 20°K, and no heat capacity anomalies were found.

15. T. F. Smith, Phys. Rev. 137 A1435 (1965), and unpublished data.

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or

B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.