Submitted to Journal of American
Ceramic Society as a Note

UCRL-18763
Preprint

cy. 2

SOLUBILITY LIMITS IN THE $MgO-Fe_2O_3$ SYSTEM AS DETERMINED BY DIFFUSION

RECEIVED
LAWRENCE
RADIATION LABORATORY

MAY 8 1969

LIBRARY AND
DOCUMENTS SECTION

Stuart L. Blank and Joseph A. Pask

April 1969

AEC Contract No. W-7405-eng-48

TWO-WEEK LOAN COPY

This is a Library Circulating Copy
which may be borrowed for two weeks.
For a personal retention copy, call
Tech. Info. Division, Ext. 5545

LAWRENCE RADIATION LABORATORY
UNIVERSITY of CALIFORNIA BERKELEY

UCRL-18763
cy. 2

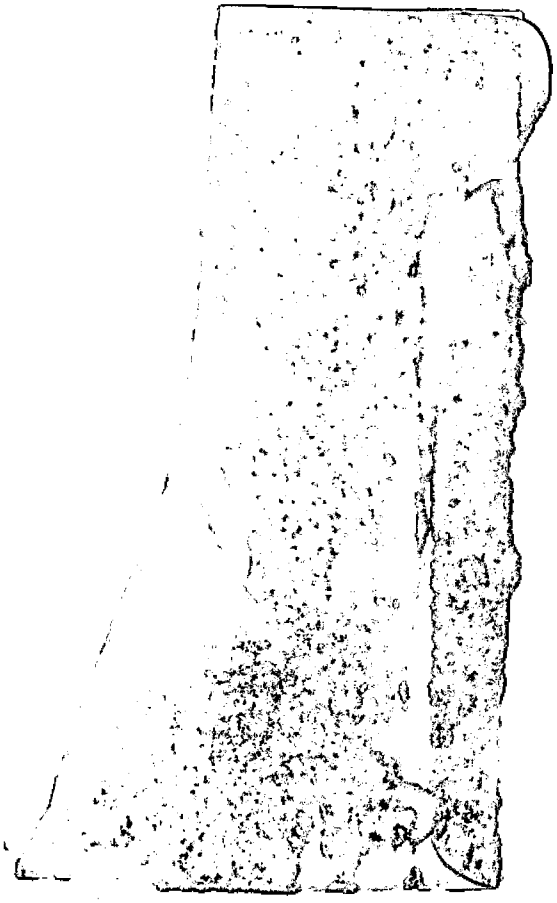

DISCLAIMER

This document was prepared as an account of work sponsored by the United States Government. While this document is believed to contain correct information, neither the United States Government nor any agency thereof, nor the Regents of the University of California, nor any of their employees, makes any warranty, express or implied, or assumes any legal responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by its trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof, or the Regents of the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof or the Regents of the University of California.

SOLUBILITY LIMITS IN THE $MgO-Fe_2O_3$ SYSTEM AS DETERMINED BY DIFFUSION

Stuart L. Blank* and Joseph A. Pask

Inorganic Materials Research Division, Lawrence Radiation Laboratory,
and Department of Materials Science and Engineering,
College of Engineering, University of California
Berkeley, California

Diffusion studies on the $MgO-Fe_2O_3$ couple provided information on the solubility limits in air. Of particular interest is the solubility of iron oxide in MgO.

A diffusion profile for Fe obtained with an electron microprobe (no differentiation between different valences of the element) at 1300°C in air for 43 hours is shown in Fig. 1.[1] The profile shows an atomic fraction of 0.063 Fe in MgO and 0.286 in magnesioferrite (subsequently referred to as ferrite) at the MgO-ferrite interface, and 0.354 Fe in ferrite and 0.400 in Fe_2O_3 at the ferrite-Fe_2O_3 interface (indicating no detectable solubility of MgO in Fe_2O_3). These are equilibrium compositions of total Fe as indicated by a number of anneals for different times at 1300°C.

The 1300°C isothermal section for the $MgO-FeO-Fe_2O_3$ system determined by Speidel is shown in Fig. 2.[2] The diagram indicates the following

This work was done under the auspices of the United States Atomic Energy Commission.

At the time this work was done, the writers were, respectively, research assistant and professor of ceramic engineering, Department of Materials Science and Engineering, and Inorganic Materials Research Division, Lawrence Radiation Laboratory, University of California.

* Now research ceramist, Bell Telephone Laboratories, Murray Hill, New Jersey.

equilibrium compositions in $10^{-0.68}$ atm oxygen (air) for ferrite: in presence of magnesiowüstite--20.0 w/o MgO, 0.2 w/o FeO, and 79.8 w/o Fe_2O_3; in presence of Fe_2O_3--7.9 w/o MgO, 16.2 w/o FeO, and 75.9 w/o Fe_2O_3. These compositions correspond to the following molar quantities: 0.994 MgO, 0.006 FeO, 1.000 Fe_2O_3 and 0.465 MgO, 0.535 FeO, 1.130 Fe_2O_3, respectively. This indicates a stoichiometric spinel composition (with a small amount of Mg^{+2} replaced by Fe^{+2}) in equilibrium with MgO. The spinel in the presence of excess Fe_2O_3, however, has more than half of the Mg^{+2} replaced by Fe^{+2} and some Fe_2O_3 in solid solution. The calculated atomic fraction of Fe, from these values, in the ferrite in equilibrium with MgO is 0.287 and with Fe_2O_3, 0.365. The corresponding values shown by the diffusion profile in Fig. 1 agree well. Consequently, the diffusion studies have supported the results for 1300°C in air reported by Speidel,[2] Willshee and White,[3] and within experimental limits by Reijnen[4] who showed a very small solubility of MgO in the spinel phase, but not by Paladino.[5]

It then can be assumed that the 0.063 atomic fraction of Fe in the MgO at the ferrite interface, shown by the diffusion profile, is the equilibrium solubility limit at 1300°C. The solubility in MgO was not determined by Speidel, but Fig. 2 does indicate that approximately 0.2 w/o FeO would be present in the MgO under these conditions. Taking this value and calculating the balance of the total Fe as Fe_2O_3 results in the following composition for the MgO phase in equilibrium with ferrite: 77.2 w/o MgO, 0.2 w/o FeO, and 22.6 w/o Fe_2O_3, or 93.0 mole % MgO, 0.14 FeO, and 6.86 Fe_2O_3. This agrees well with the value of 21.8 w/o Fe_2O_3

shown on the quasi-binary isobaric temperature-composition diagram for $MgO-Fe_2O_3$ reported by Phillips et al.[6] Using our diffusion composition as a point on the $10^{-0.68}$ isobar allows the estimation of a new boundary line indicating solubility limits in MgO at varying oxygen pressures, which is shown as the lower short-dash line in Fig. 2. The upper long-dash line appeared in Speidel's original figure.

The diffusion study also provided data for solubility limits of Fe in MgO of 0.070 atomic fraction at 1330°C, 0.086 at 1370°C, and 0.155 at 1460°C. The diffusion couples were analyzed only for diffusivities of total Fe;[1] information was not available to differentiate between relative amounts of ferrous and ferric iron.

REFERENCES

1. Stuart L. Blank and Joseph A. Pask, "Diffusion of Iron and Nickel in Magnesium Oxide Single Crystals," to be published in J. Am. Cer. Soc.

2. D. H. Speidel, "Phase Equilibria in the System $MgO-FeO-Fe_2O_3$: The 1300°C Isothermal Section and Extrapolations to Other Temperatures,: J. Am. Cer. Soc., 50 [5] 243-248 (1967).

3. J. C. Willshee and J. White, "An Investigation of Equilibrium Relationships in the System $MgO-FeO-Fe_2O_3$ up to 1750°C in Air," Trans. Brit. Ceram. Soc., 66 [11] 541-55 (1967).

4. P. Reijnen, "Phase Equilibria in the System $MgO-FeO-Fe_2O_3$", Philips Res. Repts., 23, 151-188 (1968).

5. A. E. Paladino, "Phase Equilibria in the Ferrite Region of the System $FeO-MgO-Fe_2O_3$," J. Am. Cer. Soc., 43 [4] 183-191 (1960).

6. Bert Phillips, Shigeyuki Somiya, and Arnulf Muan, "Melting Relations of Magnesium Oxide-Iron Oxide Mixtures in Air," J. Am. Cer. Soc., 44 [4] 167-169 (1961).

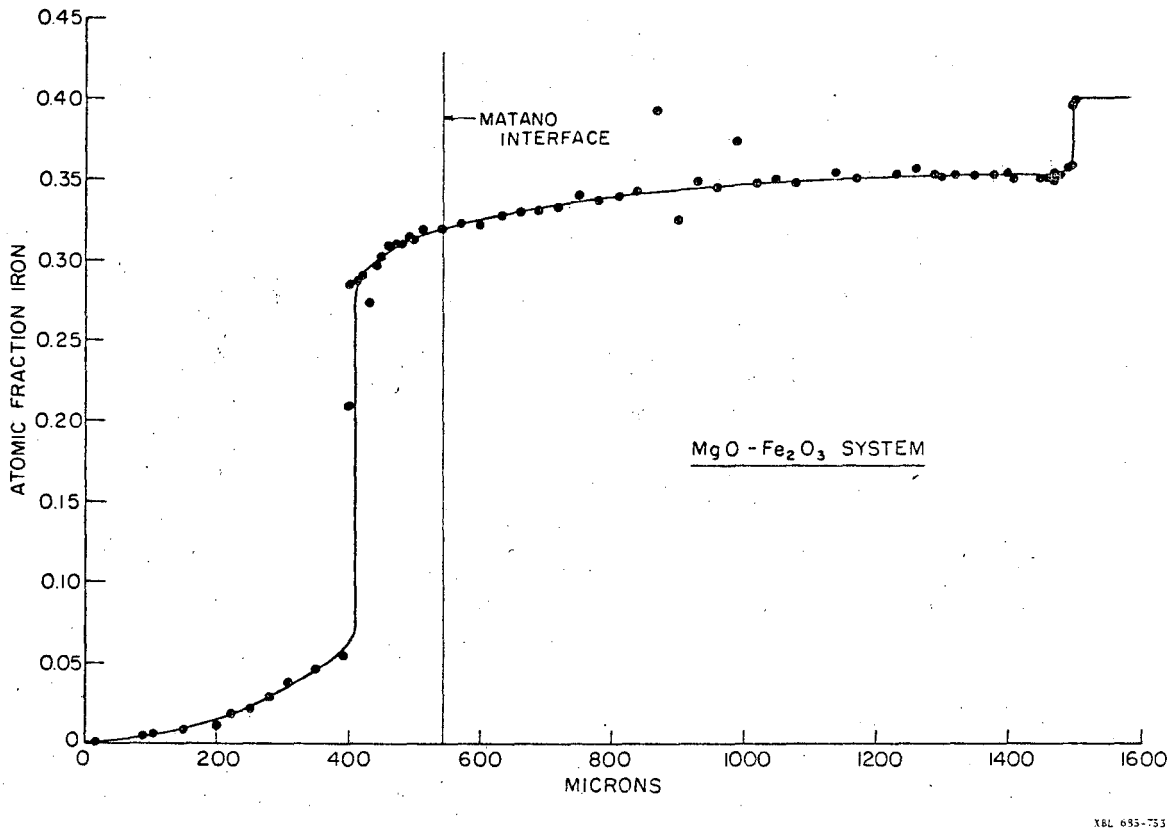

Fig. 1 Diffusion profile in the Fe_2O_3 system in air at 1300°C for 43 hours

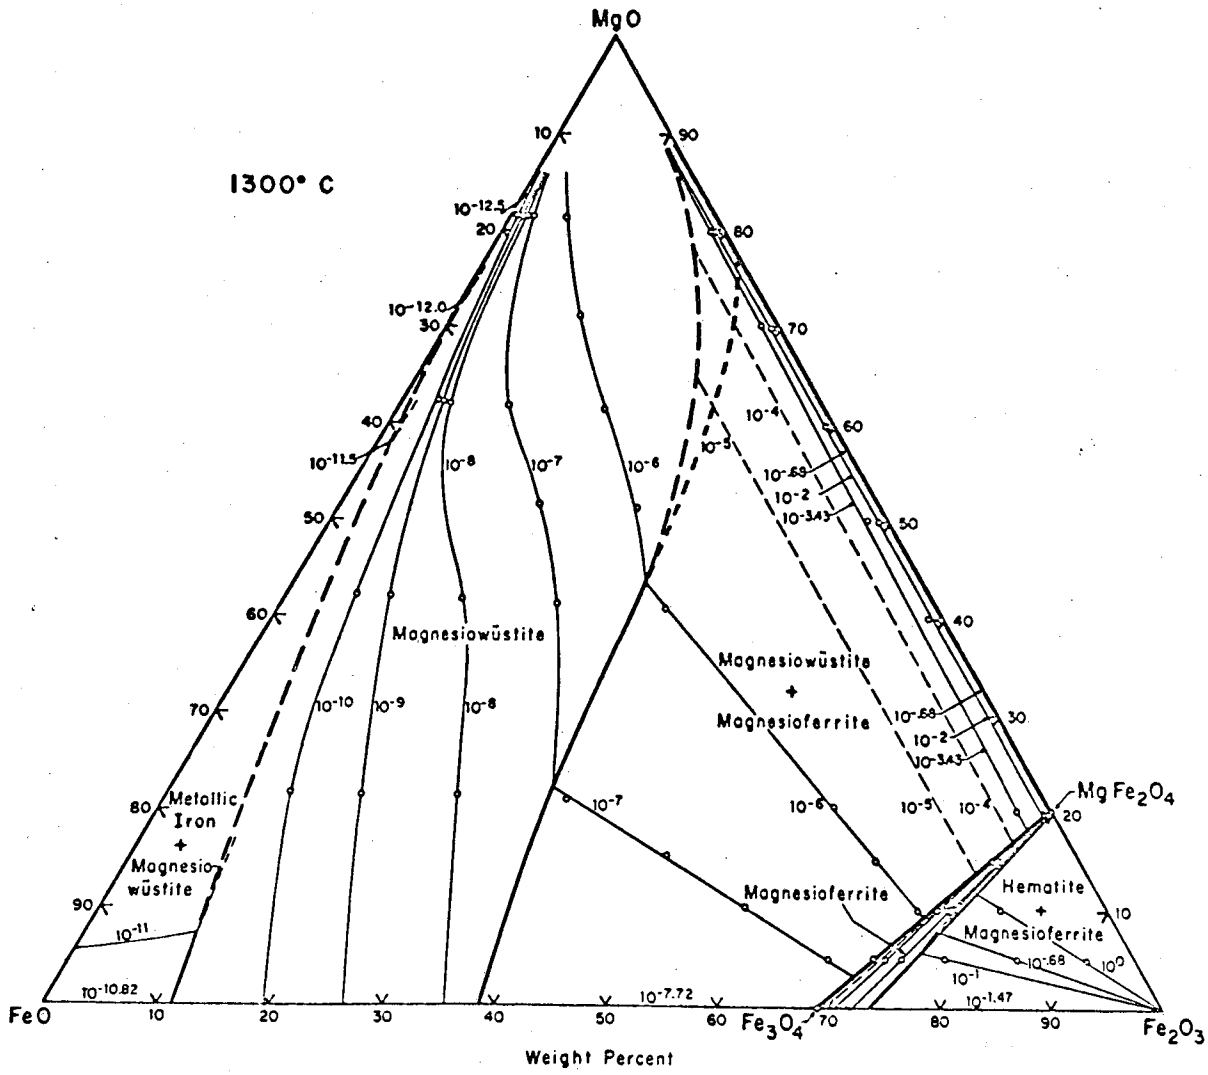

XBL 687-1334

Fig. 2 The 1300°C isothermal section for the $MgO-FeO-Fe_2O_3$ system, from Speidel,[2] with addition of lower short-dash line as discussed in text.

LEGAL NOTICE

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

A. Makes any warranty or representation, expressed or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or

B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission, or employee of such contractor, to the extent that such employee or contractor of the Commission, or employee of such contractor prepares, disseminates, or provides access to, any information pursuant to his employment or contract with the Commission, or his employment with such contractor.

TECHNICAL INFORMATION DIVISION
LAWRENCE RADIATION LABORATORY
UNIVERSITY OF CALIFORNIA
BERKELEY, CALIFORNIA 94720